

Temperature and magnetic field dependent tunneling spectroscopy of PtIr/Sr_{0.9}La_{0.1}CuO₂ point contact

L. Shan¹, H. Gao¹, Z.Y. Liu¹, Min-Seok Park², Kyung Hee Kim², C.U. Jung², Sung-Ik Lee² and H. H. Wen^{1*}

¹ National Laboratory for Superconductivity, Institute of Physics,

Chinese Academy of Sciences, P. O. Box 603, Beijing 100080, P. R. China and

² National Creative Research Initiative Center for Superconductivity and Department of Physics, Pohang University of Science and Technology, Pohang 790-784, Republic of Korea

(Dated: February 2, 2008)

Low barrier quasiparticle tunneling spectroscopy on Sr_{0.9}La_{0.1}CuO₂ has been studied with PtIr/Sr_{0.9}La_{0.1}CuO₂ point contacts at various temperatures and magnetic fields. No zero-bias conductance peaks are observed. By fitting tunneling conductance to Blonder-Tinkham-Klapwijk theory, the temperature dependent *s*-wave superconducting gaps are obtained. The present results exclude the possibility of *d*-wave symmetry for the pair gap in Sr_{0.9}La_{0.1}CuO₂, and do not support the conventional phonon mediated pairing in this system either.

PACS numbers: 74.50.+r, 74.45.+c, 74.72.-h

I. INTRODUCTION

The symmetry of the superconducting order parameter is a crucial problem in revealing the mechanism of superconductivity in cuprates. It is now generally agreed that hole-doped (*p*-type) high temperature superconducting cuprates have a $d_{x^2-y^2}$ pairing symmetry in the underdoped and optimally doped region [1, 2] while in the overdoped region a small component such as *s* or d_{xy} appears in addition to the $d_{x^2-y^2}$ order parameter [3, 4, 5, 6]. On the other hand, the $d_{x^2-y^2}$ wave symmetry in the low and optimally electron-doped (*n*-type) cuprates has also been confirmed by the recent scanning SQUID [7], tunneling [8], ARPES [9, 10], penetration depth [11, 12, 13], and specific heat experiments [14]. However, the *s*-wave symmetry is found to be dominant in the overdoped *n*-type cuprates [13, 15], which is very different from the case of *p*-type ones. Although there are significant differences between the *p*-type and *n*-type cuprates both in structure and in superconductivity, it is of general interest to see whether their behaviors can be explained within a unified physical picture. Using the exchange of antiferromagnetic spin fluctuations as the relevant pairing mechanism, Manske *et al.* [16, 17] have theoretically demonstrated the existence of the pure $d_{x^2-y^2}$ wave symmetry in underdoped *n*-type cuprates, they also successfully interpreted the well-known experimental facts such as the smaller T_c values of *n*-type cuprates than that of *p*-type ones, and why the superconductivity of *n*-type cuprates only occurs for a narrow doping range [18, 19, 20]. In Ref.[16], the electron-phonon coupling was introduced to explain the weakening of the $d_{x^2-y^2}$ pairing symmetry and the dominance of *s*-wave symmetry in overdoped *n*-type. That is, there may be some kinds of interactions coexisting and competing with each other. Recently observed nodeless gap in nearly whole

doping range of Pr_{2-x}Ce_xCuO_{4-δ} ($0.115 \leq x \leq 0.152$) superconducting films [21] also implicated that some order parameter may prevail over the others at some given conditions. Therefore, in order to understand the electronic phase diagram and the superconducting mechanism of *n*-type cuprates in whole doping range, one of the essential tasks is to confirm the possible pairing symmetry other than $d_{x^2-y^2}$ type and investigate its properties in detail.

The infinite-layer system Sr_{1-x}La_xCuO₂ is the simplest form of *n*-type cuprates. The recently synthesized single-phase samples of Sr_{0.9}La_{0.1}CuO₂ have nearly 100% superconducting volume [22], enabling reliable studies on its superconductivity. This system is of interest because of its three-dimensional superconductivity [23] and it is expected to be a good candidate showing isotropic order parameter. Recently, its *s*-wave superconductivity has been proposed by scanning tunneling microscopy (STM) [24] and specific heat [25] measurements separately. However, more detailed information is needed to clarify its pairing symmetry and superconducting mechanism.

In this work we study the quasiparticle tunneling spectroscopy of PtIr/Sr_{0.9}La_{0.1}CuO₂ point contacts. The *s*-wave pairing symmetry is demonstrated both by fitting the measured spectra to Blonder-Tinkham-Klapwijk (BTK) theory and by investigating the field induced quasiparticle states. Meanwhile, the determined temperature dependence of superconducting energy gap $\Delta(T)$ is obviously different from that of the conventional electron-phonon coupling superconductors.

II. EXPERIMENTAL METHOD

The sample studied in this work is high-density granular material of Sr_{0.9}La_{0.1}CuO₂ [22], which is the same as that reported in Refs [24, 25]. X-ray diffraction confirmed the single-phase nature of the sample and revealed random grain orientation [22]. The sample was cut into a slab with dimensions of about $2 \times 2 \times 0.5 \text{ mm}^3$. As shown

*Electronic address: hhwen@aphy.iphy.ac.cn

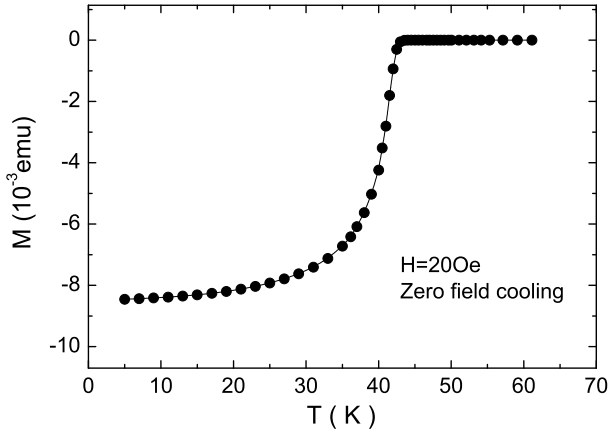


FIG. 1: Superconducting transitions measured by Dc magnetization.

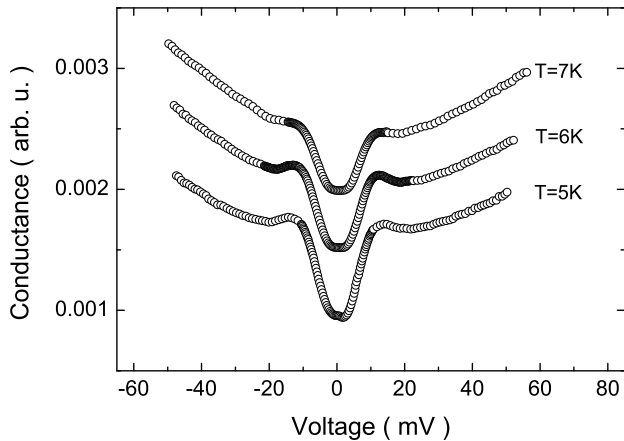


FIG. 2: Typical conductance spectra of low-barrier tunneling measurements on PtIr/Sr_{0.9}La_{0.1}CuO₂ point contacts.

in Fig. 1, the superconducting transition temperature T_c is about 43K as characterized by DC magnetization measurement. The sample surface was polished by fine metallographic grinding papers and then milled by Ar iron for 20 minutes. The PtIr tips were prepared by electrochemical etching in CaCl_2 solution using $\text{Pt}_{0.9}\text{Ir}_{0.1}$ wire with a diameter of 0.25 mm. The approaching of the tips was controlled by a differential screw. The point contact insert was set in the sample chamber of an Oxford cryogenic system Maglab. Typical four-terminal and lock-in technique were used to measure the differential resistance dV/dI vs V of the point contacts. Then the $dV/dI - V$ curves were converted into the dynamical conductance $dI/dV - V$ (or $\sigma - V$) curves.

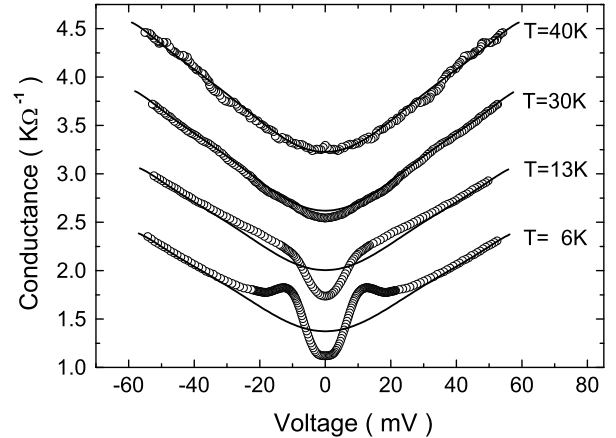


FIG. 3: An illustration of constructing normal conductance background for various temperatures according to the functional form of the spectra around T_c .

III. RESULTS AND DISCUSSION

Fig. 2 shows the typical raw data of the conductance (σ) of PtIr/Sr_{0.9}La_{0.1}CuO₂ point contact. In the following analysis, in order to reduce the uncertainty in the fitting process, we have averaged the positive and negative bias parts for all the measured spectra as shown in Fig. 3. It is noted that all the characteristics of superconductivity disappear completely at about 40K, therefore we construct the background of each spectral curve according to the functional form of the normal-state conductance (at $T=40\text{K}$), as denoted by solid lines presented in Fig. 3. All spectra are normalized by the corresponding background before fitting. The typical normalized spectra are presented in Fig. 4, denoted by open circles. It is found that all the curves for lower temperature can be well fitted with the generalized BTK theory [26] with BCS density of states (DOS), in which the quasiparticle energy E is replaced by $E + i\Gamma$, where Γ is the smearing parameter characterizing the finite lifetime of the quasiparticles [27]. For the temperature higher than 20K, the spectra are badly smeared due to the thermal effect and surface roughness, therefore, it is difficult to obtain the credible fitting parameters. Another significant result of our experiments is that no zero-bias conductance peak (ZBCP) is found in the spectra for any grain orientations. This is consistent with the results of STM [24] and has been regarded as a proof of non- d -wave pairing symmetry.

However, in some tunneling experiments, no ZBCP was observed even in the superconductors with d -wave symmetry [15, 28]. There are two possible reasons. One is the effect of disorder and the other is thermal smearing. We have examined these two effects in our data. As shown in Fig.2 of Ref.[28], when the ZBCP is suppressed by an increase of disorder in the material, the whole spectral curve becomes unfeatured, which is not

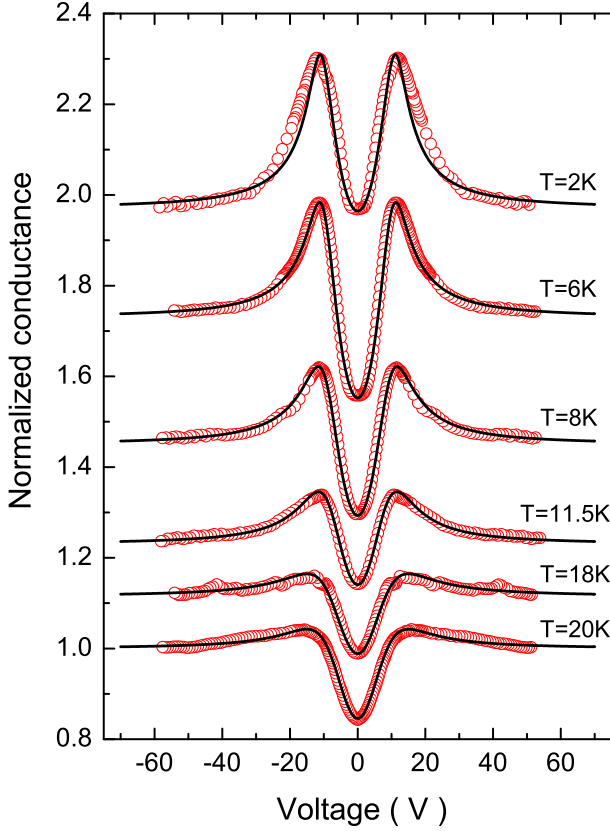


FIG. 4: Theoretically fitting the normalized conductance for various temperatures. The normalized spectra are denoted by open circles. The solid lines represent the fits to the modified BTK theory. All curves except the bottom curve have been shifted upwards for clarity.

the case in our work, i.e., although there is no ZBCP, the other characteristics of superconductivity are prominent. Furthermore, the smearing effect is quantitatively investigated by introducing a smearing factor Γ into the spectral calculations for $d_{x^2-y^2}$ symmetry. In such calculations, we adopt the same potential model and formula presented in Ref.[29]. The theoretical simulations of the spectra for two arbitrarily selected injection angles ($\theta_N = 15^\circ$ and $\theta_N = 20^\circ$) are presented in Fig. 5(b), a typical modified BTK fitting is shown in Fig. 5(a) as a comparison. It is found that although the smearing factor Γ is as large as 40% of the maximal gap Δ_{max} , the ZBCP is still prominent. Even the Γ -value is enhanced to 8meV which has been comparable to Δ_{max} , the ZBCP still exists for $\theta_N = 20^\circ$. Moreover, the depression of ZBCP is accompanied by the remarkable weakening of all the spectral features. It should also be pointed out that the ZBCP will become more pronounced when θ_N approaches to 45° . Considering the random orientations of the crystal grains, if the pairing symmetry is $d_{x^2-y^2}$ type, the measured spectra may have remarkable difference from one position to the other and the ZBCP should be easily observed at many grains. Therefore, a fully

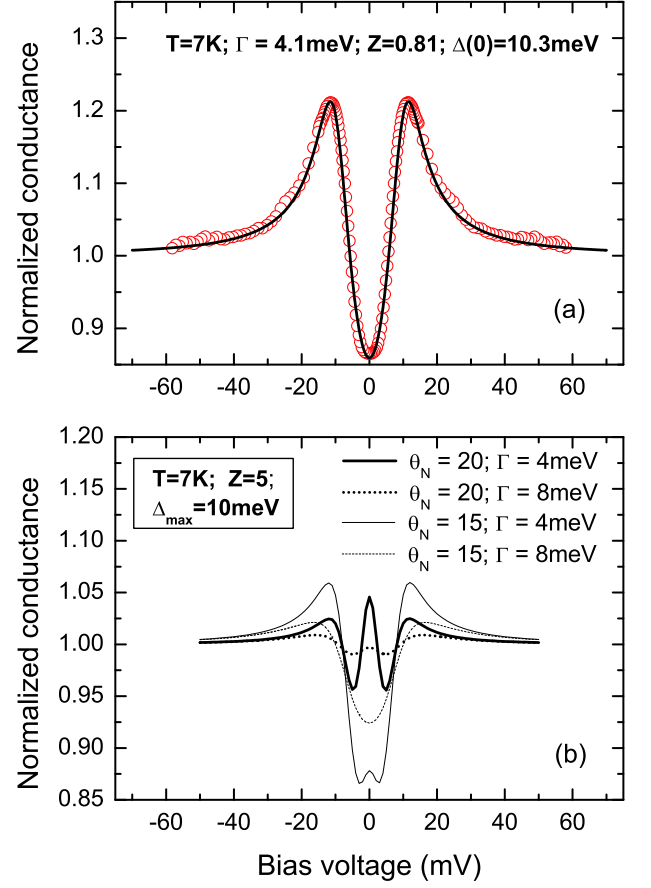


FIG. 5: (a) Adopted parameters for a typical s-wave fit to modified BTK theory. (b) Theoretical calculations for the spectra of a superconductor with $d_{x^2-y^2}$ pairing symmetry.

gapped fermi surface should be responsible for the non-existence of ZBCP in $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$.

In Fig. 6, we present the temperature dependence of superconducting gap determined by fitting the normalized conductance spectra to modified BTK theory. The theoretical prediction of electron-phonon coupling mechanism is also presented as a comparison. Although the s -wave pairing symmetry and the BCS-type quasiparticle dispersion ($E_{\pm}(k) = \pm\sqrt{\varepsilon(k)^2 + \Delta^2}$) are accepted in our fitting, the obtained superconducting gap $\Delta(T)$ obviously deviates the conventional electron-phonon coupling mechanism. The BCS-type quasiparticle dispersion has recently been observed in Bi-2212 by STM [30] and in Bi-2223 by ARPES [31]. The good agreement of theoretical fitting and the experimental results in our work indicates that the infinite-layer n -type cuprate $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ also favors such quasiparticle dispersion.

In order to get more information of superconductivity in $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$, we have measured the response of the conductance spectra to magnetic field at various temperature. In such measurements, we have pressed the tip tightly on the sample in order to make the interface large enough so as to comprise enough vortices. There-

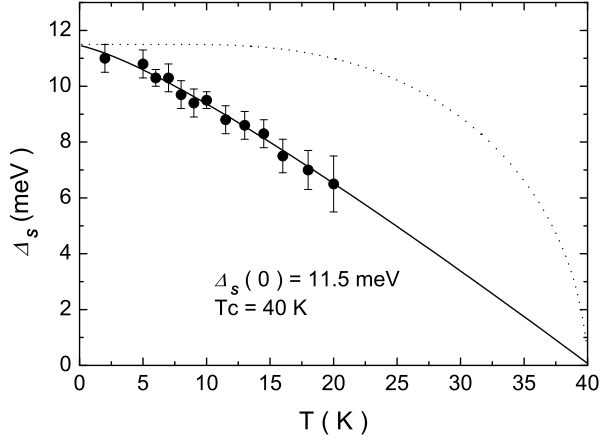


FIG. 6: The experimental energy gap (solid circles) obtained from the fits described in Fig. 4. The dotted line is the prediction of conventional electron-phonon coupling mechanism. The solid line is the guide to eyes.

fore, any spectral variation caused by the change of vortex density can be detected when the applied magnetic field is altered. If the applied field does not change the configuration of the point contact, the background should be identical for the spectra measured at different fields. From Fig. 7(a), we can see the superposition of the high bias spectra for 0T and 1T, and this is also the case for 3T and 5T. However, there is a clear difference between the background conductance of {0T, 1T} and that of {3T, 5T}, indicating that a slight shift of the tip has occurred. As a consequence, the spectral shape is transformed not only by magnetic field but also by the potential barrier between the tip and sample. Therefore, in order to investigate the field induced conductance, in the following analysis we only study the spectra with the same background conductance. Fig. 7(b) shows the difference between the conductance of 0T and 1T by open circles, and that between 3T and 5T by solid circles, these are determined by subtracting lower field data from higher field data.

It is found that the field induced conductance (reflecting the vortex states) has two common features for various temperatures. Firstly, a ZBCP occurs at low energy scale around fermi energy and enhances with increasing magnetic field; Secondly, at low field (e.g. 1T), the ZBCP splitting is observed. These two features are opposite to that of vortex states in *p*-type cuprates [32, 33], which has no ZBCP due to the appearance of field induced orders such as antiferromagnetism [34] and d-density wave [35]. Furthermore, the ZBCP splitting has not been observed around the vortex core in conventional type-II superconductors [36]. However, these features are consistent with the theoretical results for *s*-wave as reported by Wang *et al.* [37]. In their calculations, the microscopic mean-field theory was adopted and the structure of CuO₂ layers was considered. The “*s*-wave” model was supposed to

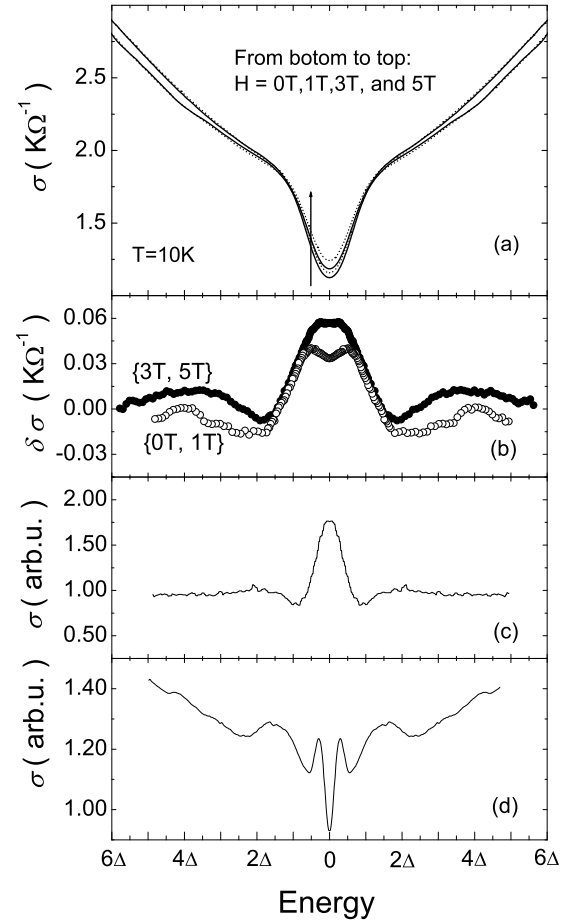


FIG. 7: (a) The typical magnetic field dependence of the tunneling spectra of PtIr/Sr_{0.9}La_{0.1}CuO₂ point contacts measured at 10K. The applied field is 5T, 3T, 1T, and 0T from top to bottom. (b) Difference between the conductance of 1T and 0T (open circles) and that of 5T and 3T (solid circles). (c) and (d) are the typical spectrum around vortex cores in conventional superconductor NbSe₂ [36] and *p*-type cuprate YBa₂Cu₃O₇ [33], respectively. The abscissa of each figure has been normalized according to the energy gap of the corresponding sample.

have on-site attraction. According to this model, a clear ZBCP is obtained at the center of the vortex cores and the split occurs when the distance between the vortices is large enough (i.e., at low field). Although this model does not consider the coupling between CuO₂ layers, its outcome is qualitatively consistent with our experimental results.

In the inset of Fig. 8, we present a set of field dependent spectra with the same background. As shown in the main frame of Fig. 8, the field induced conductance (reflecting vortex states) has been determined by subtracting the zero-field spectrum from that measured in various fields. The ZBCP splitting still can be recognized for the lowest field (1T) although the temperature is as high as 20K. It is known that the field induced quasiparticle density

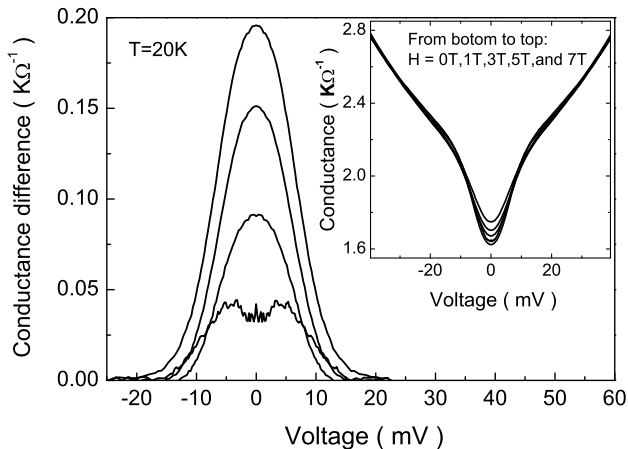


FIG. 8: Magnetic field induced conductance calculated from the raw data shown in the inset. The spectra are measured at 20K and all the curves presented here have the same background.

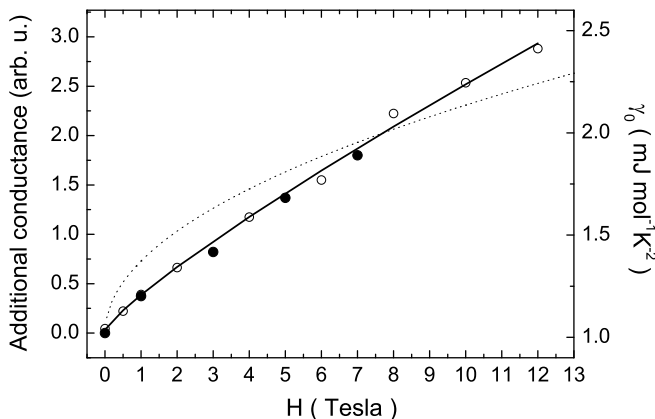


FIG. 9: The comparison between the field dependence of the additional conductance in this work (solid circles) and that of low energy quasiparticle DOS obtained from specific heat measurements (open circles). The dotted line is the prediction for clean d-wave superconductors and the solid line has the form of $y \approx H^{0.85}$.

of states (DOS) mostly comes from the exterior of the vortex cores for $d_{x^2-y^2}$ wave symmetry, while for s -wave symmetry the contribution from the interior of the cores is dominant. Since the interface between the tip and sample is large enough as we have mentioned, we have measured the total field induced DOS both the outside and the inside of the vortex cores. We have integrated the low energy additional conductance in a range of $\pm 5\text{meV}$, as shown in Fig. 9 (Two other different integral ranges of $\pm 10\text{meV}$ and $\pm 30\text{meV}$ have also been selected and the obtained rules are the same as reported here). As a comparison, we present the magnetic field dependent

low energy DOS of $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ determined by specific heat measurements [25]. The results reported here are in good agreement with the specific heat measurements, i.e., the field induced low energy DOS can be described as $y \approx H^m$ with $m = 0.85$. It is well known that the exponent m should be 0.5 for clean d -wave superconductors and 1 for s -wave superconductors in simple limit. However, m may deviate these two values in the case of dirty d -wave [38] or in the case of s -wave considering the vortex lattice effect [39]. Ref.[25] has ruled out the possibility of dirty d -wave and adopted that $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ is a s -wave superconductor, which is in good agreement with our forementioned conclusions. It should be pointed out that our result in Fig. 9 is derived from the data measured at 20K which is higher than that ($< 7K$) in Ref.[25]. However, in the case of s -wave symmetry, the field dependence of additional DOS is mainly determined by the density of vortices instead of temperature. Considering the much lower magnetic field than the upper critical field and $T_c \approx 40K \gg 20K$ in our investigations, the conclusion presented in Fig. 9 is reasonable and self-consistent.

IV. CONCLUDING REMARKS

In summary, we have performed low-barrier quasiparticle tunneling measurements on the $\text{PtIr}/\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$ point contacts in detail. No ZBCP is observed on the randomly oriented crystal grains. All the normalized conductance spectra can be well fitted in the frame of BTK theory, providing an impelling evidence for the BSC-type s -wave superconductivity in $\text{Sr}_{0.9}\text{La}_{0.1}\text{CuO}_2$. This is also proved by investigating the magnetic field induced vortex states. However, it is noted that the temperature dependence of superconducting gap deviates from the prediction of conventional electron-phonon coupling mechanism, and the field induced ZBCP is splitted at low field. These features can not be interpreted in the frame of conventional superconducting mechanism, therefore, cautious must be taken to associate the experimentally observed s -wave superconductivity in overdoped n -type cuprates with the electron-phonon mechanism.

Acknowledgments

This work is supported by the National Science Foundation of China (NSFC 19825111, 10074078), the Ministry of Science and Technology of China (project: nkbrsf-g1999064602), and Chinese Academy of Sciences with the Knowledge Innovation Project. The work in Pohang University is supported by the Ministry of Science and Technology of Korea through the Creative Initiative Program.

-
- [1] C. C. Tsuei and J. R. Kirtley, *Rev. Mod. Phys.* **72**, 969 (2000).
- [2] D. J. VanHarlingen, *Rev. Mod. Phys.* **67**, 515 (1995).
- [3] N. -C. Yeh, C. -T. Chen, G. Hammerl, J. Mannhart, A. Schmehl, C. W. Schneider, R. R. Schulz, S. Tajima, K. Yoshida, D. Garrigus, and M. Strasik, *Phys. Rev. Lett.* **87**, 087003 (2001).
- [4] M. Vojta, Y. Zhang, and S. Sachdev, *Phys. Rev. Lett.* **85**, 4940 (2000).
- [5] D.V. Khveshchenko and J. Paaske, *Phys. Rev. Lett.* **86**, 4672 (2001).
- [6] G. Sangiovanni, M. Capone, S. Caprara, C. Castellani, C. Di Castro, and M. Grilli, *Phys. Rev. B* **67**, 174507 (2003), and references therein.
- [7] C.C. Tsuei and J. R. Kirtley, *Phys. Rev. Lett.* **85**, 182 (2000).
- [8] A. Biswas, P. Fournier, V. N. Smolyaninova, R. C. Budhani, J. S. Higgins, and R. L. Greene, *Phys. Rev. B* **64**, 104519 (2001).
- [9] T. Sato, T. Kamiyama, T. Takahashi, K. Kurahashi, and K. Yamada, *Science* **291**, 1517 (2001).
- [10] N. P. Armitage, D. H. Lu, D. L. Feng, C. Kim, A. Damascelli, K. M. Shen, F. Ronning, Z.-X. Shen, Y. Onose, Y. Taguchi, and Y. Tokura, *Phys. Rev. Lett.* **86**, 1126 (2001).
- [11] J. D. Kokales, P. Fournier, L. V. Mercaldo, V. V. Talanov, R. L. Greene, and S. M. Anlage, *Phys. Rev. Lett.* **85**, 3696 (2000).
- [12] R. Prozorov, R.W. Giannetta, P. Fournier and R. L. Greene, *Phys. Rev. Lett.* **85**, 3700 (2000).
- [13] J. A. Skinta, M. S. Kim, T. R. Lemberger, T. Greibe and M. Naito, *Phys. Rev. Lett.* **88**, 207005 (2002).
- [14] H. Balci, V. N. Smolyaninova, P. Fournier, Amlan Biswas, and R. L. Greene, *Phys. Rev. B* **66**, 174510 (2002).
- [15] A. Biswas, P. Fournier, M. M. Qazilbash, V. N. Smolyaninova, H. Balci, and R. L. Greene, *Phys. Rev. Lett.* **88**, 207004 (2002).
- [16] D. Manske, I. Eremin, and K. H. Bennemann, *Phys. Rev. B* **62**, 13922 (2000).
- [17] D. Manske, I. Eremin, and K. H. Bennemann, *Phys. Rev. B* **67**, 134520 (2003), and references therein.
- [18] Y. Tokura, H. Takagi, and S. Uchida, *Nature (London)* **337**, 345 (1989).
- [19] H. Takagi, S. Uchida, and Y. Tokura, *Phys. Rev. Lett.* **62**, 1197 (1989).
- [20] J. L. Peng, E. Maiser, T. Venkatesan, R. L. Greene, and G. Czjzek, *Phys. Rev. B* **55**, R6145 (1997).
- [21] M. S. Kim, J. A. Skinta, T. R. Lemberger, A. Tsukada and M. Naito, *Phys. Rev. Lett.* **91**, 087001 (2003).
- [22] C. U. Jung, J. Y. Kim, M. S. Kim, M. S. Park, H. J. Kim, Y. Yao, S. Y. Lee and S. I. Lee, *Physica C* **366**, 299 (2002); *Phys. Rev. B* **65**, 172501 (2002).
- [23] Mun-Seog Kim, C. U. Jung, J. Y. Kim, Jae-Hyuk Choi and Sung-Ik Lee, *Solid State Commun.* **123**, 17 (2002).
- [24] C. T. Chen, P. Seneor, N. C. Yeh, R. P. Vasquez, L. D. Bell, C. U. Jung, J. Y. Kim, M. S. Park, H. J. Kim, and S. I. Lee, *Phys. Rev. Lett.* **88**, 227002 (2002).
- [25] Z. Y. Liu, H. H. Wen, L. Shan, H.P. Yang, X. F. Lu, H. Gao, C.U. Jung, J. Y. Kim, M. S. Park, H. J. Kim, and S. I. Lee, *cond-matt/0306238*.
- [26] G.E. Blonder, M. Tinkham, and T.M. Klapwijk, *Phys. Rev. B* **25**, 4515 (1982).
- [27] A. Pleceník, M. Grajcar, S. Benacka, P. Seidel and A. Pfuch, *Phys. Rev. B* **49**, 10016 (1994).
- [28] M. Aprili, M. Covington, E. Paraoanu, B. Niedermeier, and L. H. Greene, *Phys. Rev. B* **57**, R8139 (1998).
- [29] S. Kashiwaya, Y. Tanaka, M. Koyanagi, and K. Kajimura, *Phys. Rev. B* **53**, 2667 (1996).
- [30] J. E. Hoffman, K. McElroy, D. H. Lee, K. M. Lang, H. Eisaki, S. Uchida, and J. C. Davis, *Science* **297**, 1148 (2002).
- [31] H. Matsui, T. Sato, T. Takahashi, S. C. Wang, H. B. Yang, H. Ding, T. Fujii, T. Watanabe, and A. Matsuda, *cond-matt/0304505*.
- [32] S. H. Pan, E.W. Hudson, A. K. Gupta, K.-W. Ng, H. Eisaki, S. Uchida, and J. C. Davis, *Phys. Rev. Lett.* **85**, 1536 (2000).
- [33] I. Maggio-Aprile, Ch. Renner, A. Erb, E. Walker, and ϕ . Fischer, *Phys. Rev. Lett.* **75**, 2754 (1995).
- [34] H. Tsuchiura, M. Ogata, Y. Tanaka, and S. Kashiwaya, *Phys. Rev. B* **68**, 012509 (2003), and references therein.
- [35] M. M. Maška and M. Mierzejewski, *Phys. Rev. B* **68**, 024513 (2003), and references therein.
- [36] H. F. Hess, R. B. Robinson, R. C. Dynes, J. M. Valles, Jr., and J. V. Waszczak, *Phys. Rev. Lett.* **62**, 214 (1989).
- [37] Y. Wang, and A. H. MacDonald, *Phys. Rev. B* **52**, R3876 (1995).
- [38] C. Kübert, P. J. Hirschfeld, *Solid State Commun.* **105**, 459 (1998).
- [39] M. Ichioka, A. Hasegawa, and K. Machida, *Phys. Rev. B*, **59**, 184 (1999).